



Radiation Hardness Studies of Cooling Fluids Epoxies and Capacitors for CMS Pixel System

M. Atac^{a**}, B. Gobbi^b, L. Cremaldi^c, J. Hoffman^a

^aFermi National Accelerator Laboratory*, Batavia IL 60510, USA

^bNorthwestern University, Evanston IL, USA

^cUniversity of Mississippi, USA

Abstract

Radiation hardness studies of C₆F₁₄ Fluorinert (FC72) fluid, some epoxies and Tantalum capacitors were studied for the CMS (Compact Muon Solenoidal) experiment at the LHC (Large Hadron Collider) of CERN. For a successful operation of Forward Silicon Pixel Tracker of the CMS, the cooling fluid, epoxies to be used and the filter capacitors of bias voltage supplies need to be radiation hard. It was also necessary to find out whether the cooling fluid would dissociate under the expected fluence and damage Beryllium cooling channels of the Forward Silicon Pixel Discs. This paper is a report of our findings from the performed tests.

PACS No. 29.40.Gx CMS Pixel Tracking System

** Email: matac@fnal.gov, Phone No. 630-840-3960.

* Work supported by U. S. Department of Energy under contract no. DE-AC02-76CH0300.

1. Introduction

The Silicon Vertex Tracker of the CMS Detector [Reference 1] is going to play an important role in determining impact parameters of the b and c quark decays and for pattern recognition, especially for identifying high p_t electron and muon tracks within jets. A perspective view of the pixel vertex tracker is shown in Figure 1. It shows two layers of barrel pixels and two forward pixel discs. We are planning to have three layers of barrel pixel system and three pixel discs on each side. This is necessary for decay vertex determinations and pattern recognition to sufficient efficiency. Three-point determination of tracks can be considered a minimal requirement.

The pixel size of the pixel tracking system is chosen to be $150\mu\text{m} \times 150\mu\text{m}$ size, with a total number of about 18 million pixels on the forward discs. Each and every pixel will be flip-chip bump bonded to the same size of readout electronics. There may be 106 transistors in each matching circuitry; therefore requiring a very efficient cooling system. The total power dissipation is estimated to be about 1.4kW, together with the peripheral electronic circuitry. We plan to run the tracker at a temperature of -12°C . A Beryllium cooling tube and Beryllium panel structure were chosen for their mechanical strength and for minimizing the

amount of radiation length of materials in the way of charge particle tracks. We plan to circulate C_6F_{14} (FC72) Fluorocarbon liquid as coolant due to its good heat capacity. Our radiation test results showed that this would be a good choice. Coolants containing water would be corrosive to Beryllium (Be) and Aluminum (Al); therefore such coolants should be avoided. We were concerned about FC72 dissociating and interacting with Be and therefore we carried out the following tests.

2. Radiation Damage Tests

A 3cm diameter, 9gram Be-disc was placed into a glass jar containing the FC72 cooling fluid. The cap of the jar had polyethylene lining. The weight of the Be-disc was taken using a high precision scale before and after exposing to 20MegaRAD of Co^{60} per cm^2 irradiation in a facility at Purdue University. The level of irradiation is sufficient for 5-10 year LHC running time, due to the reason that only small fraction of the coolant will be exposed to irradiation. There will be a coolant reservoir away from the CMS detector. The precision of the scale was better than 0.01 milligram. The disc was left in the liquid for 3 weeks before scaling its weight after the irradiation. There was no measurable change in the weight of the disc after this period. An optical picture of the Be-disc was taken before and after the irradiation and we did not see any visible change of the surface quality. A

photo of the Be-disc together with a magnified view is shown in Figure 2. The magnified view shows the machine grooves with no visible residue in them. The FC72 Fluorocarbon is a very clear transparent liquid. The color of the liquid after the irradiation was as clear as before, but the glass jar became very black as shown in Figure 3. The irradiated liquid was sent to a commercial company [Reference 2] to look for traces of Beryllium and Fluoride Ion. Less than 1ppm of Beryllium (this is the precision of the company's measurement) and 17ppm of Fluoride-Ion (F^-) traces were found by the company.

Fermilab has a well-equipped material research facility. Epoxy radiation damage tests were also carried out using the facility. Some selected epoxies with different viscosity were used for the shear tests. Five samples of epoxy joints between silicon wafer and small Carbon fiber composite plates were prepared for their shear strength testing before irradiating and after irradiating them using Co^{60} sources to a radiation level of 20 MegaRAD per cm^2 . The results are summarized in Figures 4 and 5. The results indicate that the shear strength is somewhat better after the irradiation. We believe that this is due to more hardening of the epoxies in time. The viscosities of the epoxies just after mixing the two components are given in Figure 5. We are convinced that these selected epoxies

will provide plenty of strength for gluing flip-chip bump bonded pixel chips to the Beryllium substrates.

Some Tantalum capacitors were exposed to fluence of 2×10^{14} 63 MeV protons at the UC-Davis cyclotron. The value of the capacitors and the breakdown voltages were not measurably altered at this radiation level.

3. Conclusions

We are convinced that the cooling fluid, epoxies and capacitors will survive at the LHC luminosities of the CMS pixel system. We plan doing further test of the pixel-mounted units under realistic conditions.

4. Acknowledgements

The authors would like to express their appreciation to Drs. D. Pellett and R. Lander of UC-Davis for their help in Proton irradiation, to D. Burke and B. Sizemore of Fermilab for their contribution to shear strength measurement of the epoxies, to R. Tilden for his help in designing the pixel structure and to G. Sellberg for his many contributions to the silicon pixel project of the CMS experiment.

5. References

1. CMS Technical Design Report; CERN/LHCC 98-6, CMS TDR 5, 15 April 1998.
2. Fitzsimmons and Associates, Inc., West Chicago, IL.

Disclaimer

Operated by Universities Research Association Inc. under
Contract No. DE-AC02-76CH03000 with the United States Department of Energy.

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

Approved for public release; further dissemination unlimited.

6. Figure Captions


Figure 1. A perspective figure of the pixel tracker of the CMS. It shows two layers of barrel pixels and two forward discs. We plan to have three barrel layers and three forward discs in the final configuration.



Figure 2. Surface pictures of the Beryllium disc after irradiation (a) full disc surface and (b) the magnified portion the surface. Magnified view shows that machined grooves were not covered with any residue.





Figure 3. Photos of the glass jar (a) before and (b) after irradiation. It shows how dark in color the glass jar became after the irradiation.

Figure 4. An average summary of the scatter plot of the shear test results before and after the irradiation of the various epoxies. With the exception of one epoxy, they show some increase in the shear strength. This could be due to more hardening of the epoxies in time.



Figure 5. A histogram plot of the results. It shows that there are small variations in five samples for each epoxy.

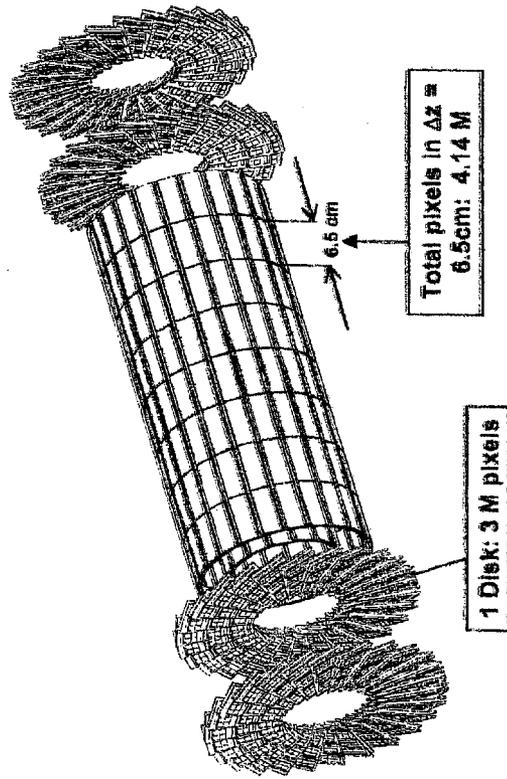

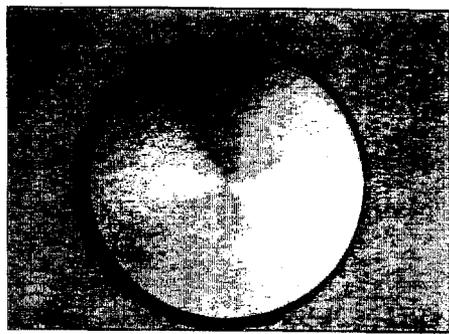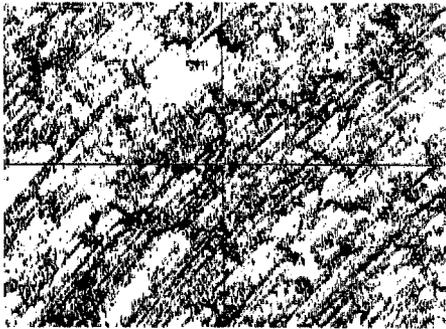

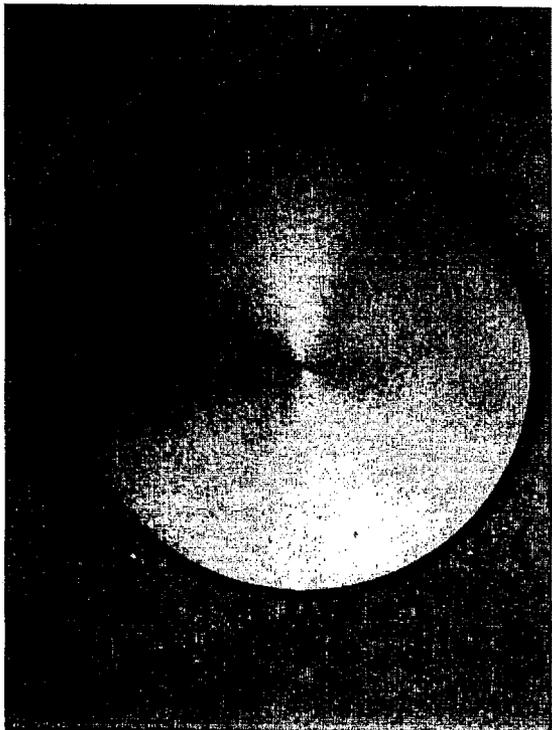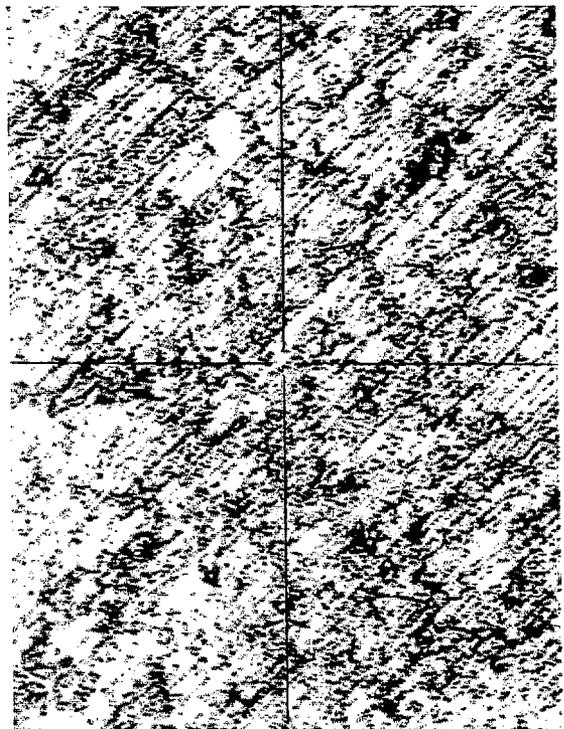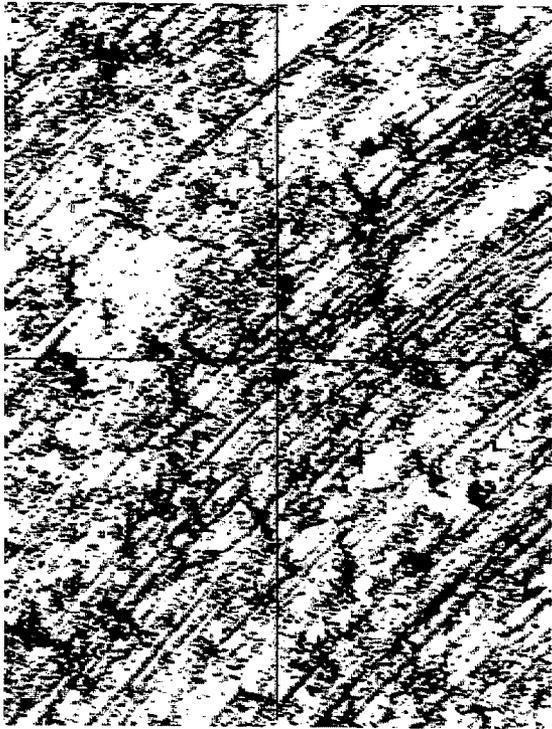




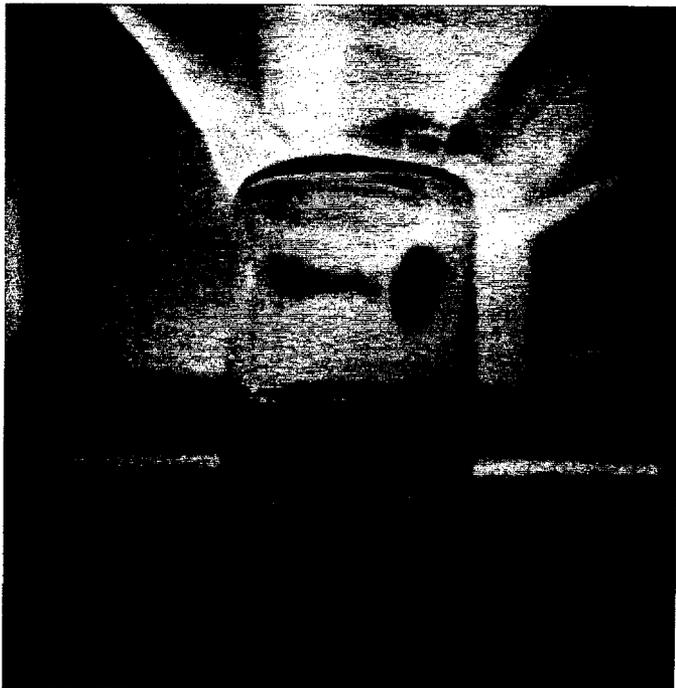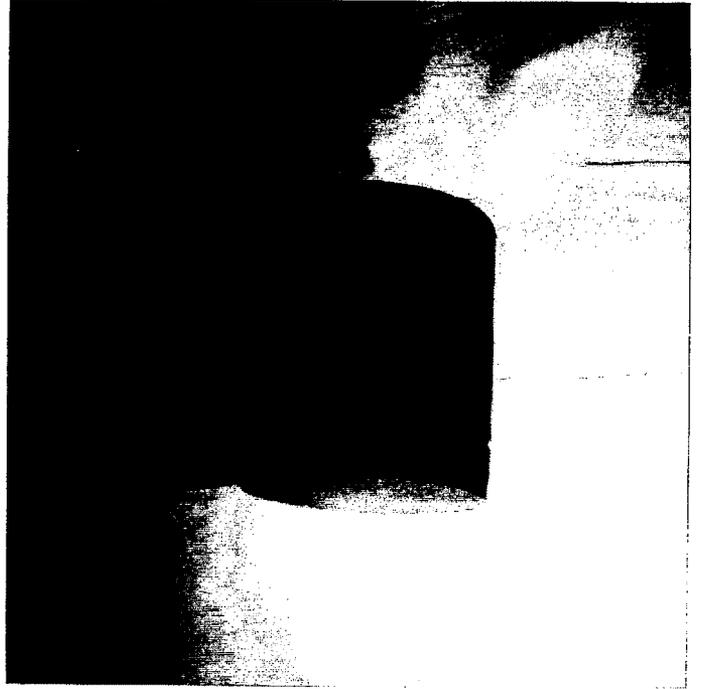

Shear Force to Break [PSI]

- Before irradiation
- After irradi., 10^7 rads Co^{60}

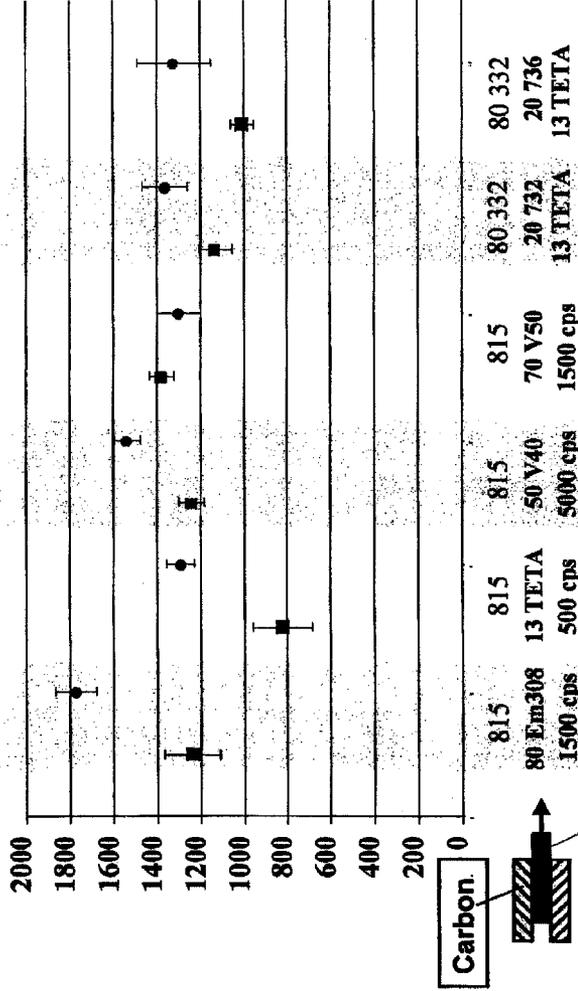

Carbon



Silicon

FNAL: M. ATAC, J. Hoffman

