

## MEASUREMENTS AT SLAC ON SUPERCONDUCTING NIOBIUM CAVITIES AND STRUCTURES\*

P. B. Wilson, M. A. Allen, H. Deruyter, Z. D. Farkas, H. A. Hogg, E. W. Hoyt, H. L. Martin and M. Rabinowitz  
Stanford Linear Accelerator Center, Stanford University, Stanford, California 94305

(presented by P. B. Wilson)

### Abstract

Tests are continuing at SLAC on superconducting niobium cavities and structures at S- and X-band frequencies. Peak electric and magnetic fields on the order of 20 MV/m and 400 G have been obtained in a TM mode cavity at 2.85 GHz with unloaded Q's at high fields on the order of  $10^{10}$ . These fields and Q's are adequate for superconducting RF systems for high energy storage rings and recirculating linear accelerators.

### A. Introduction

Long range plans at SLAC include the possibility of converting the present accelerator to a 100 GeV superconducting linac. The proposed energy gradient (33 MV/m) would require a traveling-wave resonant superconducting structure capable of sustaining peak RF electric and magnetic fields on the order of 55 MV/m and 1000 G. While fields of this order have been demonstrated in single cavities at X-band, formidable technological difficulties still remain to be overcome before the construction of a high-gradient accelerator on this large a scale can be realized. Recently, other SLAC improvement projects that might lead to applications of RF superconductivity in the more immediate future have been suggested. For example, it has been proposed<sup>1)</sup> that the energy and duty cycle of the SLAC accelerator be increased by storing the beam and then recirculating it a second time through the existing linac. This machine, termed a recirculating linear accelerator (RLA), would initially be constructed to store and recirculate the beam at 17.5 GeV. At present it is planned to use a conventional RF system, consisting of a 200 m length of disk-loaded accelerating structure, to provide an energy gain of 150 MeV per turn for the proposed RLA. Because of the rapid increase in synchrotron radiation loss with increasing recirculation energy, it is not practical to upgrade the RLA to the final design energy of 25 GeV using a conventional RF system. However, a superconducting RF system only 30 m in length would provide the required additional energy gain of 450 MeV per turn. The accelerating gradient would be 7.5 MV/m, assuming two passes per turn in opposite directions through a standing wave structure. The peak fields in the structure would be on the order of 340 G and 19 MV/m.

High energy storage rings are also under consideration at SLAC<sup>2)</sup> and elsewhere. In such an application an energy gradient on the order of 4 MV/m, requiring peak fields of about 180 G and 10 MV/m, would be satisfactory. The superconducting accelerator development effort at SLAC is now directed toward the development of superconducting structures which can meet the relatively modest energy gradients required by the RLA and high energy storage rings.

Until recently most of the superconducting cavity measurements at SLAC have been made at X-band. A summary of experimental results obtained to February of this year was recently published.<sup>3)</sup> Residual Q's

\*Supported by the U.S. Atomic Energy Commission.

exceeding  $10^{11}$  and peak RF magnetic fields on the order of 1000 G were attained in a TE<sub>011</sub> mode cavity operating at 10.5 GHz. Since this date measurements on X-band cavities have continued, but the principal measurement results have been obtained on S-band cavities and structures.

### B. X-Band Tests

Although any superconducting accelerator or RF system constructed at SLAC will operate at S-band frequency (or lower), it remains convenient to test new ideas concerning materials or fabrication and processing techniques using small X-band cavities. A second electron-beam welded TE<sub>011</sub> mode cavity, similar to the one which gave the good results reported previously,<sup>3)</sup> has been made. The initial test results were not outstanding (a residual Q of  $5 \times 10^9$  and magnetic breakdown field of 240 G were obtained), but the behavior of the surface resistance as a function of field level was quite interesting (see Fig. 1).

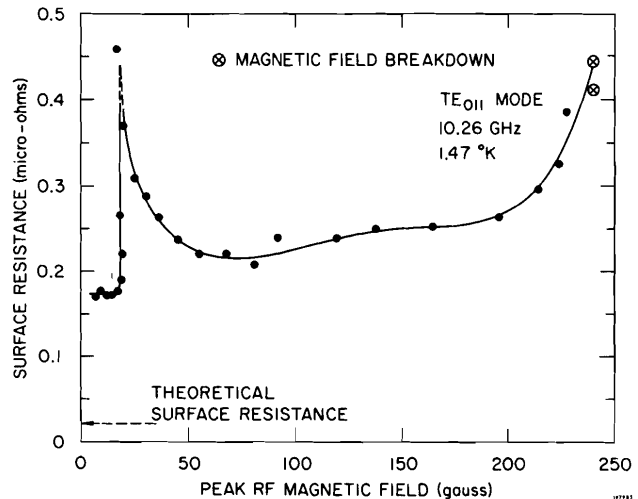


FIG. 1--Surface resistance as a function of RF magnetic field level for TE-mode X-band cavity (test no. 44).

As has been the case for most previous tests on X-band cavities operating in the residual loss region, a rather sharp increase in surface resistance by about a factor of two is observed at an RF magnetic field of about 20 G. In the case of the test shown in Fig. 1, the low field edge of the absorption peak is very sharp, while the high field edge is less so. Halbritter<sup>4)</sup> has suggested that increased absorption can be expected as the result of surface states at an RF magnetic field level given by  $H(G) = 4f(\text{GHz})$ , or at about 40 G for a frequency of 10 GHz. The shape of the peak in Fig. 1 can be explained by the fact that no increase in absorption takes place until the field reaches some critical level at the location of the maximum field within the cavity. If the resonance is sharp, the increase in loss will be sharp. As the field is increased further, however, other portions of the cavity gradually experience

the loss enhancement but with decreasing effect on the total loss, which could lead to an asymmetric absorption peak having the form shown by the data in Fig. 1.

Two TM X-band cavities were fabricated and tested, but with very poor results ( $Q_0 \approx 10^7$ ). It is felt that the low Q's are a result of either the technique used to electron-beam weld the cavity halves together, or the impurity content of the niobium. Tests are in progress to distinguish between the two possibilities.

C. S-Band Tests

An extensive series of tests was made at 2.85 GHz on the cavity shown in Fig. 2. The cavity was machined

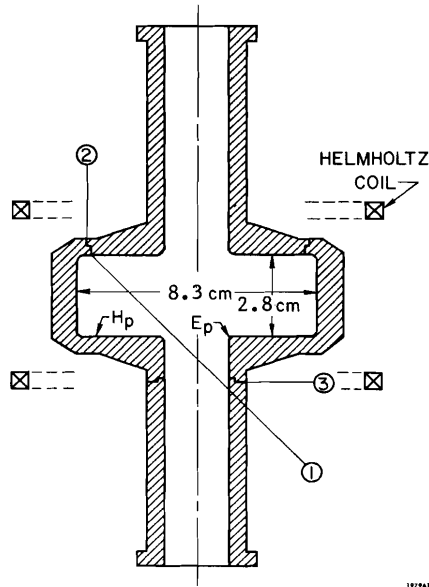


FIG. 2--TM-mode S-band niobium cavity. Numbers indicate location and order of electron-beam welds.

in three separate pieces from a solid bar of niobium. The pieces were then joined together by electron-beam welding using the welding sequence shown in Fig. 2. The locations of the peak electric and magnetic fields ( $E_p$  and  $H_p$ ) are also shown. The fields were determined in terms of the unloaded cavity Q and power dissipation, using the LALA program<sup>5</sup>) adapted for the SLAC 360/91 computer, to be  $H_p(G) = 1.08 \times 10^{-2} (Q_0 P)^{1/2}$ , and  $H_p/E_p = 18.4 \text{ G/MV/m}$ .

The experimental results obtained for this cavity are given in Table I (see next page). The results of all tests made on this cavity to date, successful or otherwise, are listed. Several tests can be singled out for more detailed discussion. Figure 3 shows the variation of surface resistance as a function of field level for the test in which the highest magnetic breakdown field was reached. In Table II the values of the Q and the peak fields are given. By processing at a peak electric field of about 20 MV/m, the Q was increased by about a factor of two. Peak magnetic and electric fields of 420 G and 23 MV/m were attained at magnetic field breakdown after processing. Radiation indicated the presence of field emission, however, and after some minutes of operation at field levels

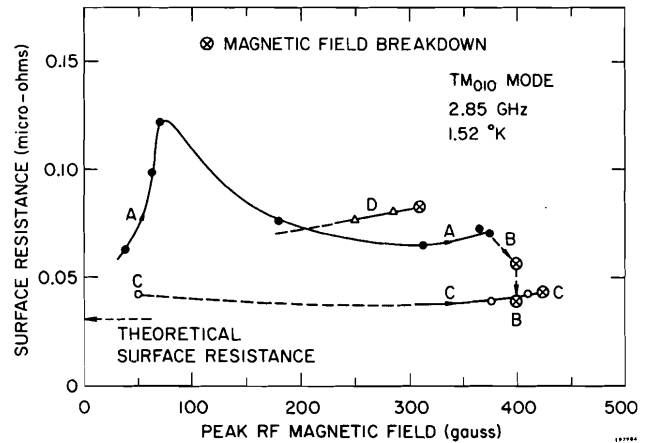


FIG. 3--Surface resistance as a function of RF magnetic field level for TM-mode S-band cavity (test no. 2). Curve A: initial application of high power. Curve B: decrease in surface resistance during processing. Curve C: behavior after processing. Curve D: behavior after Q degradation.

TABLE II  
Measurement Results for TM Mode S-Band Cavity (Test #2)

	$Q_0$	$H_p$ (G)	$E_p$ (MV/m)	Remarks
Initial results at low power	$3.2 \times 10^9$	40	2.2	
Results at high power before processing	2.9	374	20.3	Some radiation observed
Results after processing:				
Low power	4.8	50	2.6	
High power	4.6	424	23.1	Magnetic field breakdown
Results after Q degradation	2.4	311	16.9	Magnetic field breakdown

close to breakdown, the cavity suddenly experienced a degradation both in Q and in the breakdown field level. Subsequent cavity behavior was then stable at the new field level (310 G and 17 MV/m). Note also the peak in Curve A at about 70 G. The peak seems to be too far from the predicted field level to be explained by magnetic surface states.

Tests 11 through 14 give results obtained by cooling the cavity down in an external dc magnetic field applied using the Helmholtz coil mounted as shown in Fig. 2. The currents in the two coils were in opposition so that the applied field was radial and maximum at the surface of the cavity in the plane of symmetry normal to the cavity axis. Figure 4 shows the surface resistance as a function of the maximum applied d.c. magnetic field at the cavity surface, assuming that the field distribution does not change as the cavity goes superconducting. There is no simple way to measure the amount of flux which is actually trapped, or the distribution of the trapped flux over the cavity surface in the superconducting state. With this uncertainty understood Fig. 4 shows an attempt to determine the enhancement of the surface resistance due to the applied field. The total surface resistance ( $R_{tot}$ ) can be considered to be the sum of a theoretical surface resistance,

TABLE I  
Measurement Results for TM Mode S-Band Cavity (2848 MHz)

Tests	$Q_0$ at Low Power	$Q_0$ at $H_p$	$H_p$ (gauss)	$E_p$ (MV/m)	Remarks
1--After initial etch and high temperature firing.	$6 \times 10^8$ ( $1.56^\circ$ K)	$2 \times 10^8$ ( $1.56^\circ$ K)	140*	7.6	Cavity surface looks poor (dust and roughness). Some radiation.
2--Cavity re-etched and re-fired. See also Table II.	$4.8 \times 10^9$ ( $1.54^\circ$ K)	$4.6 \times 10^9$ ( $1.54^\circ$ K)	424*	23.1	Cavity underwent degradation during operation at $E_p$ .
3--Cavity re-etched and re-fired.	-----	$4.7 \times 10^9$ ( $1.60^\circ$ K)	45	2.4	Apparent helium leak limited field.
4--Cavity etched lightly and re-fired.	$9.7 \times 10^9$ ( $1.52^\circ$ K)	$5.7 \times 10^9$ ( $1.52^\circ$ K)	255*	13.9	
5--Repeat of previous test. Lower ambient dc magnetic field.	$2.9 \times 10^9$ ( $1.52^\circ$ K)	$5.6 \times 10^9$ ( $1.52^\circ$ K)	245*	13.3	
6--Cavity re-etched and re-fired.	$\approx 10^{10}$	-----	---	---	Erratic behavior. Either poor rf connection or helium leak.
7--Cavity re-fired without etch.	$1.8 \times 10^{10}$ ( $1.49^\circ$ K)	$1.9 \times 10^{10}$	380*	20.7	
8--Repeat of previous test.	$1.9 \times 10^{10}$ ( $1.63^\circ$ K)	$2.3 \times 10^{10}$ ( $1.63^\circ$ K)	383*	20.8	Life test: cavity operated several hours at $H_p \approx 350$ G
9--Repeat of previous test.	-----	$1.7 \times 10^{10}$ ( $1.79^\circ$ K)	388*	21.1	Life test: $\approx 5$ hours at $H_p = 300-380$ G
10--Helmholtz coil installed. $H_{dc} = 1.5$ mG	-----	$1.2 \times 10^{10}$ ( $1.85^\circ$ K)	388*	21.1	Life test: several hours at $H_p \approx 350$ G.
11--Cooled down in $H_{dc} = 1$ G.	-----	$1.6-2.7 \times 10^9$ ( $1.46^\circ$ K)	170-280	9.2-15.2	Unable to reach breakdown field due to strong variation of frequency with rf field level.
12--Cooled down in $H_{dc} = 300$ mG.	$1.1 \times 10^{10}$ ( $1.57^\circ$ K)	$1.1-1.7 \times 10^{10}$ ( $1.57^\circ$ K)	390*-409*	21.2-22.2	
13--Cooled down in $H_{dc} = 100$ mG	$1.5 \times 10^{10}$ ( $1.49^\circ$ K)	$2.1 \times 10^{10}$ ( $1.50^\circ$ K)	386*	21.0	
14--Cooled down in $H_{dc} = 30$ mG	$1.8 \times 10^{10}$ ( $1.52^\circ$ K)	$2.1-1.4 \times 10^{10}$ ( $1.51^\circ$ K)	315-386*	21.0	
15--Attempt at nitriding. Exposed to $N_2$ for 24 minutes at $340^\circ$ C and $8 \times 10^{-5}$ torr.	$5 \times 10^8$ ( $1.57^\circ$ K)	$6 \times 10^8$ ( $1.60^\circ$ K)	205*	11.8	Nitriding done with poor base pressure ( $5 \times 10^{-6}$ torr).
16--Repeat previous test.	-----	$5 \times 10^8$ ( $1.60^\circ$ K)	186*	10.1	
17--Cavity exposed to air for 60 minutes	$1.3 \times 10^8$ ( $1.50^\circ$ K)	$2 \times 10^8$ ( $1.50^\circ$ K)	166*	9.0	
18--Cavity etched only, not fired.	$1.8 \times 10^8$ ( $1.60^\circ$ K)	$1.1 \times 10^8$ ( $1.65^\circ$ K)	208*	11.3	

\* Indicates magnetic field breakdown.

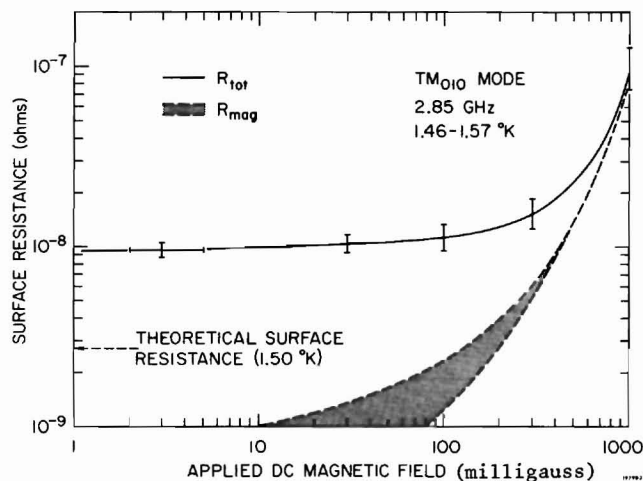


FIG. 4--Surface resistance as a function of applied d. c. magnetic field. Shaded area between dashed curves gives range for the additional residual loss due to the d. c. magnetic field.

plus a residual resistance due to nonmagnetic losses, plus a component ( $R_{mag}$ ) due to the loss introduced by trapped magnetic flux. The result of subtracting the theoretical and nonmagnetic residual loss from the total loss is shown in Fig. 4. The total loss is shown by the solid line. Each experimental point is given as a range in surface resistance, since in addition to experimental uncertainties the surface resistance varies considerably with RF field level. The shaded area gives the range in  $R_{mag}$  obtained by subtracting total nonmagnetic surface resistances of  $0.9 \times 10^{-8}$  and  $1.0 \times 10^{-9}$  ohms. At high d. c. magnetic field levels,  $R_{mag}$  appears to vary approximately as  $H_{d.c.}^2$ . At low d. c. field levels, using the limits given by the shaded area in Fig. 4, the functional dependence of  $R_{mag}$  on  $H_{d.c.}$  seems to lie between  $H_{d.c.}^{0.5}$  and  $H_{d.c.}^0$ . Accurate and extensive measurements would be needed to pin this dependence down more precisely. However, from a practical standpoint, if a superconducting accelerator operating at 1.85° K is shielded against d. c. magnetic fields to a level of less than 10 mG, the loss enhancement by trapped magnetic flux should be negligible.

From Table II it is also seen that the presence of trapped d. c. magnetic flux did not result in a decrease in the RF magnetic breakdown field, at least up to  $H_{d.c.} = 300$  mG. It was not possible to reach magnetic breakdown at  $H_{d.c.} = 1$  G because the cavity resonance became highly nonlinear; that is, the resonant frequency was strongly dependent on RF field level. The shift in resonant frequency was about  $\Delta f = -40$  Hz at  $H_{RF} = 100$  G, and appeared to be proportional to  $H_{RF}^2$ . At this field level the frequency shift was much greater than that produced by radiation pressure. This result can perhaps be explained if the effective volume of an oscillating fluxoid<sup>6)</sup> increases with the amplitude of the oscillation.

A two cell disk-loaded niobium cavity (Tadpole II) is being tested. A drawing of the cavity is given in Fig. 5. As in the case of the TM mode S-band cavity, the structure was machined from solid material and electron-beam welded together as shown in the diagram. Two modes can be excited in the structure, a symmetric and an antisymmetric mode. In the symmetric mode the

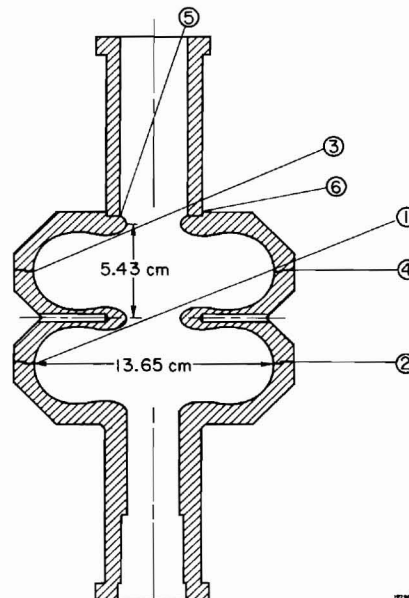


FIG. 5--Two cell niobium S-band test structure (Tadpole II). Numbers indicate location and order of electron-beam welds.

fields are in phase in the two cells (0-like mode), and the peak electric field at the surface is maximum at the shoulder of the cut-off holes. It is nearly as high on the bulgy part of the central disk, but very low at the very tip of the disk. In the antisymmetric mode the fields have opposite phases in the two cells ( $\pi$ -like mode), and the peak electric field at the surface occurs just off the tip of the central disk, although it is nearly as high at the shoulders of the cut-off tubes.

The general inability to reach 1000 G RF magnetic breakdown field at frequencies below X-band has not yet been satisfactorily explained. One possibility being explored at SLAC is that larger cavity structures are not cooled sufficiently uniformly through the transition temperature region. Thermoelectric voltages generated by the Thomson effect and the Seebeck effect (between adjacent crystals and across the boundaries between superconducting and normal regions) could give rise to large currents on the cavity surfaces with the concomitant trapping of magnetic flux. Pierce<sup>7)</sup> has considered the problem in lead-plated copper cavities. Attempts are being made to cool S-band cavities very slowly, minimizing temperature gradients as the transition is made to the superconducting state.

#### D. Conclusion

The tests made at SLAC so far on a superconducting niobium S-band cavity are encouraging in that Q's and fields have been obtained which would be adequate for superconducting RF systems applicable to high energy storage rings and recirculating linear accelerators. However, many problems concerning the stability and reproducibility of cavity properties under the fabrication, installation and operating conditions required for a full scale superconducting linac remain to be solved. In particular, it would be highly desirable to find some method for stabilizing the niobium surface against the degradation produced by oxygen and other potential contaminants,

either by coating the surface or by reacting the surface with some material to form an inert surface layer. Such a layer, of course, must not result in an appreciable degradation in the cavity Q or breakdown field. Toward this end, work is in progress at SLAC to investigate the formation and properties of surface layers of niobium nitride and niobium carbide. The search will continue to find still other materials or techniques which might contribute to the production of a more stable surface under the conditions to be expected for an operational accelerator.

#### References

1. W. B. Herrmannsfeldt, M. A. Allen, R. H. Helm, G. A. Loew, R. B. Neal and P. B. Wilson, "Recirculation of the SLAC beam," paper submitted to this conference. Also Report No. SLAC-PUB-966.
2. C. Pellegrini, D. Mohl, J. Rees, B. Richter, M. Schwartz and A. Sessler, "A high energy proton-electron-positron colliding beam system," paper submitted to this conference. Also Report No. SLAC-PUB-967.
3. M. A. Allen, Z. D. Farkas, H. A. Hogg, E. W. Hoyt and P. B. Wilson, IEEE Trans. Nucl. Sci NS-18, No. 3, 168 (1971).
4. J. Halbritter, "Dependence of surface resistance on field level in pure superconductors," External Report 3/70-14, Institut fur Experimentelle Kernphysik, Karlsruhe, West Germany.
5. H. C. Hoyt, D. D. Simmons and W. F. Rich, Rev. Sci. Instr. 37, 755 (1966).
6. M. Rabinowitz, J. Appl. Phys. 42, 88 (1971).
7. J. M. Pierce, Stanford University High Energy Physics Laboratory, Report No. 514, June 1967.

#### DISCUSSION

M. McASHAN : Is the low-field peak observed in the surface resistance a reversible effect ?  
Is it observed in decreasing as well as increasing field ?

P.B. WILSON : Yes, it is. It shows up in the emitted power decay curve (decreasing field) as a sharp discontinuity in slope.

H. HAHN : Do you need a magnetic shield against the earth's magnetic field ?

P.B. WILSON : Yes, since the earth's magnetic field is about half a Gauss, and at this field level fig. 4 shows that the cavity Q has deteriorated by more than a factor of two. However, based on these measurements, the shielding requirements are not stringent; shielding to a field level of 30 mG or so should be adequate for operation at 1.85° K.

C. JONES : Is it true that you have only tried chemical polishing and UHV annealing ?

P.B. WILSON : Yes. We have tried electropolishing on samples but not yet on a cavity.

G. SAXON : Do you propose to do measurements at other frequencies than S-band ?

P.B. WILSON : If we convert SLAC to a superconducting linac, or if a recirculating device is built at SLAC, the operating frequency will be 2856 MHz. Therefore our present measurements are being made mainly at this frequency. However, high-energy electron storage rings would require an RF system that operates at a much lower frequency. We are interested in doing structure design studies and measurements on superconducting cavities at frequencies appropriate for such rings.